

**P-05-100**

## **Forsmark site investigation**

### **Borehole KFM05A**

#### **Triaxial compression test of intact rock**

Lars Jacobsson

SP Swedish National Testing and Research Institute

August 2005

**Svensk Kärnbränslehantering AB**

Swedish Nuclear Fuel  
and Waste Management Co  
Box 5864

SE-102 40 Stockholm Sweden

Tel 08-459 84 00

+46 8 459 84 00

Fax 08-661 57 19

+46 8 661 57 19



## **Forsmark site investigation**

### **Borehole KFM05A**

#### **Triaxial compression test of intact rock**

Lars Jacobsson

SP Swedish National Testing and Research Institute

August 2005

*Keywords:* Rock mechanics, Triaxial compression test, Elasticity parameters, Stress-strain curve, Post-failure behaviour, AP PF 400-04-080.

This report concerns a study which was conducted for SKB. The conclusions and viewpoints presented in the report are those of the author and do not necessarily coincide with those of the client.

A pdf version of this document can be downloaded from [www.skb.se](http://www.skb.se)

## Abstract

Triaxial compression tests with constant confining pressure, containing the complete loading response beyond compressive failure, so called post-failure tests, were carried out on 8 water saturated specimens of intact rock from borehole KFM05A in Forsmark. The cylindrical specimens were taken from drill cores at two depth levels ranging between 329–333 m and 572–576 m borehole length. The rock type was medium-grained granite. The elastic properties, represented by Young's modulus and the Poisson ratio, and the compressive strength were deduced from these tests. The wet density of the specimens was determined prior to the mechanical tests. The specimens were photographed before and after the mechanical testing.

The measured densities for the water saturated specimens were in the range 2,590–2,710 kg/m<sup>3</sup>, which yields a mean value of 2,648 kg/m<sup>3</sup>. Three confining pressure levels were used, 5, 10 and 20 MPa, and the peak values of the axial compressive stress were in the range 289.2–488.5 MPa. The elastic parameters were determined at a load corresponding to 50% of the failure load, and it was found that Young's modulus was in the range 75.0–85.4 GPa with a mean value of 78.8 GPa and the Poisson ratio was in the range 0.15–0.20 with a mean value of 0.18. It was seen from the mechanical tests that the material in the specimens responded in a brittle way.

## Sammanfattning

Triaxiella kompressionsprov med belastning upp till brott och efter brott, så kallade ”post-failure tests”, har genomförts på 8 stycken vattenmättade cylindriska provobjekt av intakt berg. Provobjekten har tagits från en borrhärlängd från borrhål KFM05A i Forsmark vid två djupnivåer, 329–333 m och 572–576 m borrhållslängd. Bergarten vid dessa nivåer var medelkornig granit. De elastiska egenskaperna, representerade av elasticitetsmodulen och Poissons tal, har bestämts ur försöken. Bergmaterialets densitet i vått tillstånd hos proverna mättes upp före de mekaniska proven. Provobjekten fotograferades både före och efter de mekaniska proven.

Den uppmätta densiteten hos de vattenmättade proven var mellan 2 590–2 710 kg/m<sup>3</sup> med ett medelvärde på 2 648 kg/m<sup>3</sup>. Tre olika celltryck användes vid triaxialproven, 5, 10 och 20 MPa, och toppvärdena för den axiella kompressiva spänningen låg mellan 289,2–488,5 MPa. De elastiska parametrarna bestämdes vid en last motsvarande 50 % av topplasten vilket gav en elasticitetsmodul mellan 75,0–85,4 GPa med ett medelvärde på 78,8 GPa och Poissons tal mellan 0,15–0,20 med ett medelvärde på 0,18. Vid belastningsförsöken kunde man se att materialet i provobjekten hade ett sprött beteende.

# Contents

<b>1</b>	<b>Introduction</b>	7
<b>2</b>	<b>Objective and scope</b>	9
<b>3</b>	<b>Equipment</b>	11
3.1	Specimen preparation and density measurement	11
3.2	Mechanical testing	11
<b>4</b>	<b>Execution</b>	13
4.1	Description of the specimens	13
4.2	Specimen preparation and density measurements	13
4.3	Mechanical testing	14
4.4	Data handling	15
4.5	Analyses and interpretation	15
4.6	Nonconformities	17
<b>5</b>	<b>Results</b>	19
5.1	Description and presentation of the specimen	19
5.2	Results for the entire test series	36
	<b>References</b>	39
	<b>Appendix A</b>	41
	<b>Appendix B</b>	43

# 1 Introduction

Triaxial compression tests, with loading beyond the failure point into the post-failure regime, have been conducted on water-saturated specimens sampled from borehole KFM05A in Forsmark, see map in Figure 1-1. These tests belong to one of the activities performed as part of the site investigation in the Forsmark area managed by the Swedish Nuclear Fuel and Waste Management Co (SKB). The tests were carried out in the material and rock mechanics laboratories at the department of Building Technology and Mechanics at the Swedish National Testing and Research Institute (SP). All work was performed in accordance with the activity plan AP PS 400-04-080 (SKB internal controlling document) and is controlled by SP-QD 13.1 (SP internal quality document).

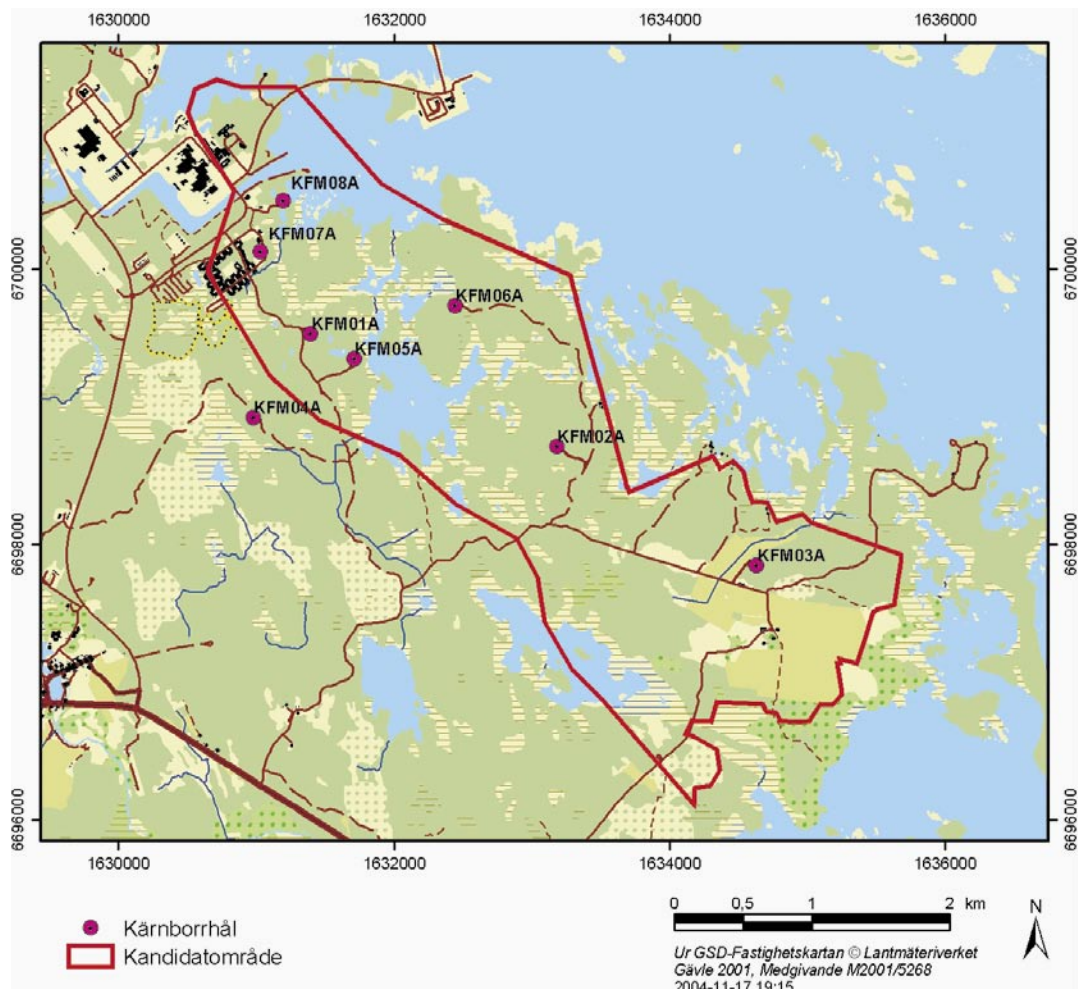


Figure 1-1. Location of the borehole KFM05A at the Forsmark site.

SKB supplied SP with rock cores which arrived at SP in September 2004 and were tested during December 2004. Cylindrical specimens were cut from the cores and selected based on the preliminary core logging with the strategy to primarily investigate the properties of the dominant rock type. The method description SKB MD 190.003, version 2.0, (SKB internal controlling document) was followed both for the sampling and for the triaxial compression tests whereas the density determinations were performed in accordance with method description SKB MD 160.002, version 2.0, (SKB internal controlling document). As to the specimen preparation, the end surfaces on the specimens were grinded in order to comply with the required shape tolerances and kept stored in water, with a minimum of 7 days, up to testing. This yields a water saturation, which is intended to resemble the in-situ moisture condition. The density was determined on each specimen and the triaxial compression tests were carried out at this moisture condition at different confining pressures. The specimens were photographed before and after the mechanical testing.

The triaxial compression tests were carried out using radial strain as the feed-back signal in order to obtain the complete response in the post-failure regime on brittle specimens as described in the method description SKB MD 190.003 and in the ISRM suggested method /1/. The axial  $\varepsilon_a$  and radial strain  $\varepsilon_r$  together with the axial stress  $\sigma_a$  were recorded during the test. The peak value of the axial compressive stress  $\sigma_c$  was determined at each test. Furthermore, two elasticity parameters, Young's modulus  $E$  and Poisson ratio  $\nu$ , were deduced from the tangent properties at 50% of the peak load. Diagrams with the volumetric and crack volumetric strain versus axial stress are reported. These diagrams can be used to determine crack initiation stress  $\sigma_i$  and the crack damage stress  $\sigma_d$ , cf /2, 3/.

## 2 Objective and scope

The purpose of the testing was to determine the compressive strength and the elastic properties, represented by Young's modulus and the Poisson ratio, of confined cylindrical intact rock cores at different confining pressures. Moreover, the specimens had a water content corresponding to the in-situ conditions. The loading was carried out into the post-failure regime in order to study the mechanical behaviour of the rock after cracking thereby enabling determine the brittleness and residual strength. The specimens are collected from borehole KFM05A, a telescopic borehole inclined c 60° from the horizontal plane and with a drilling length of c 1,000 m. Drill cores were produced within the interval c 100–1,000 m.

The results from the tests are to be used in the site descriptive rock mechanics model, which will be established for the candidate area selected for site investigations at Forsmark.



## 3 Equipment

### 3.1 Specimen preparation and density measurement

A circular saw with a diamond blade was used to cut the specimens to their final lengths. The surfaces were then grinded after cutting in a grinding machine in order to achieve a high-quality surface for the axial loading that complies with the required tolerances. The measurements of the specimen dimensions were made with a sliding calliper. Furthermore, the tolerances were checked by means of a dial indicator and a stone face plate. The specimen preparation is carried out in accordance with ASTM 4543-01 /4/.

The specimens and the water were weighed using a scale for weight measurements. A thermometer was used for the water temperature measurements. The calculated wet density was determined with an uncertainty of  $\pm 4 \text{ kg/m}^3$ .


### 3.2 Mechanical testing

The mechanical tests were carried out in a servo controlled testing machine specially designed for rock tests, see Figure 3-1. The system consists of a load frame, a hydraulic pump unit, a controller unit and various sensors. The communication with the controller unit is attained by special testing software run on a PC connected to the controller. The load frame is characterized by a high stiffness and is supplied with a fast responding actuator, cf the ISRM suggested method /1/. Furthermore, the sensors, the controller and the servo valve are rapidly responding components. The machine is equipped with a pressure vessel in which the specimens are tested under a confinement pressure. A thin rubber membrane is mounted on the specimen in order to seal it from the oil used as the confinement medium, cf Figure 3-2. The axial load is determined using a load cell, which is located inside the pressure vessel and with a maximum capacity of 1.5 MN. The uncertainty of the load measurement is less than 1%.


The axial and circumferential (radial) deformation of the rock specimen was measured. The rock deformation measurement systems are based on miniature LVDTs with a measurement range of  $\pm 2.5 \text{ mm}$ . The LVDTs were calibrated by means of a micrometer and they displayed an accuracy of  $\pm 2.5\%$  within a  $\pm 2 \text{ mm}$  range that was used in the tests. The axial deformation measurement system comprises two aluminium rings attached on the specimen, placed approximately at  $\frac{1}{4}$  and  $\frac{3}{4}$  of the specimen height, cf Figures 3-2 and 4-1. Two LVDTs mounted on the rings are used to measure the distance change between the rings on opposite sides of the specimen. The rings are supplied with three adjustable spring-loaded screws, each with a rounded tip pointing towards the specimen with 120 degrees division. The rings are mounted directly on the rubber membrane. The pre-load of the screws fixates the rings. The position of the frame piston was also stored during the test in order to permit a possibility for comparison with the measurements made with the measurement system that was based on the displacement of the rings.

The radial deformation was obtained by using a chain mounted around the specimen at mid-height, see Figure 3-2. The change of the chain-opening gap was measured by means of one LVDT and the circumferential and thereby also the radial deformation could be obtained. See Appendix A.

The specimens were photographed with a 4.0 Mega pixel digital camera at highest resolution and the photographs were stored in a jpeg-format.

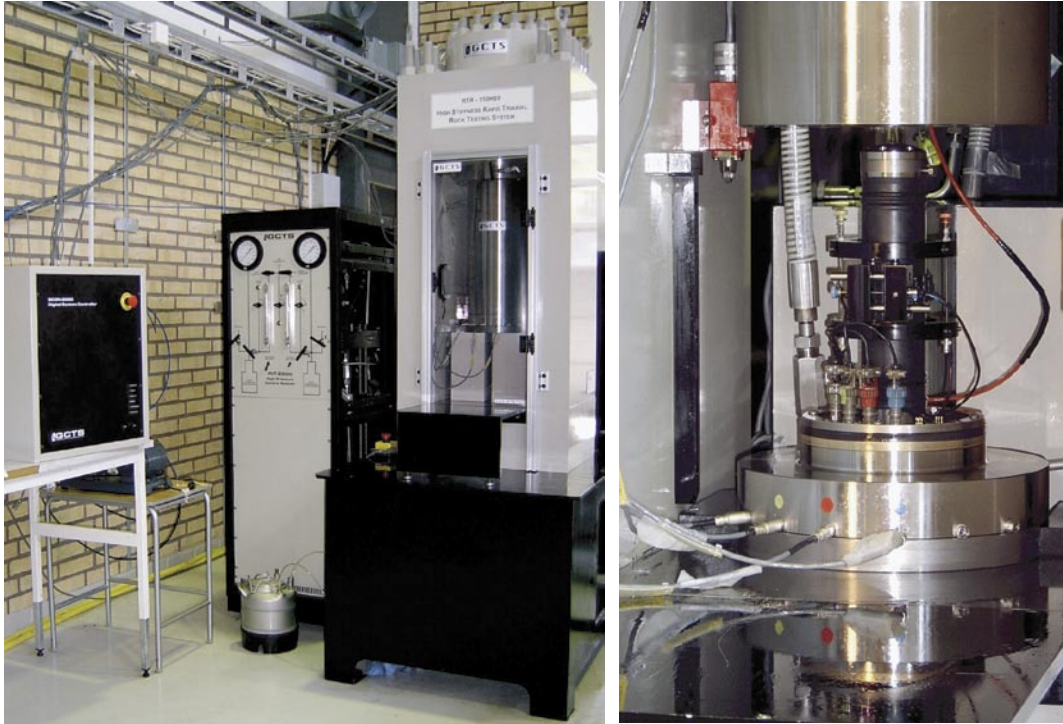

**Figure 3-1.** Left: Digital controller unit, pressure cabinet with a cell pressure intensifier and oil reservoir inside, and the load frame with closed cell (pressure vessel). Right: Bottom of the cell is lowered. The specimen is instrumented and ready for inserting in the cell.

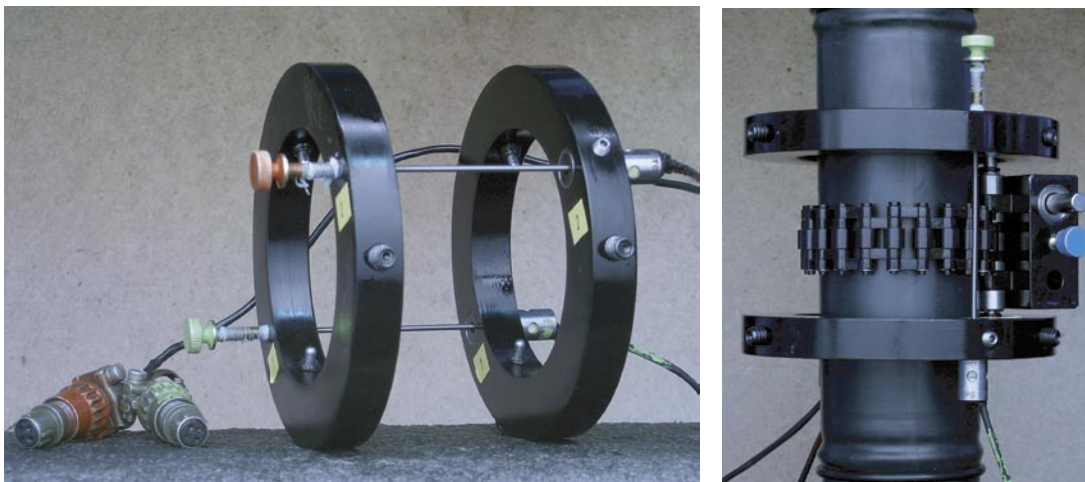

**Figure 3-2.** Left: Rings and LVDTs for axial deformation measurement. Right: Specimen and loading plates sealed with a rubber membrane. Devices for axial and circumferential deformation measurements are attached.

## 4 Execution

The water saturation and determination of the density of the wet specimens were made in accordance with the method description SKB MD 160.002, version 2.0, (SKB internal controlling document). This includes determination of density in accordance to ISRM /5/ and water saturation by SS EN 13755 /6/. The triaxial compression tests were carried out in compliance with the method description SKB MD 190.003, version 2.0, (SKB internal controlling document). The test method is based on the ISRM suggested methods /1/ and /7/.

### 4.1 Description of the specimens

The rock type characterisation was made according to Strähle /8/ using the SKB mapping (Boremap). The identification marks, upper and lower sampling depth (Secup and Seclow) and the rock type are shown in Table 4-1.

**Table 4-1. Specimen identification, sampling depth (borehole length), confining pressure at the triaxial tests and rock type for all specimens.**

Identification	Secup (m)	Seclow (m)	Confining pressure (MPa)	Rock type
KFM05A-115-1	329.43	329.56	5	Medium-grained granite
KFM05A-115-2	329.57	329.70	10	(All specimens)
KFM05A-115-3	330.00	330.14	10	
KFM05A-115-4	332.75	332.89	20	
KFM05A-115-6	572.68	572.82	5	
KFM05A-115-7	572.82	572.96	10	
KFM05A-115-8	573.11	573.25	10	
KFM05A-115-10	575.55	575.68	20	

### 4.2 Specimen preparation and density measurements

The temperature of the water was 19.5°C, which equals to a water density of 998.3 kg/m<sup>3</sup>, when the determination of the wet density of the rock specimens was carried out. Further, the specimens had been stored for 20 days in water when the density was determined.

A step-by step description of the general procedure for the specimen preparation and the density measurement is as follows.

Step	Activity
1	The drill cores were marked where the specimens are to be taken.
2	The specimens were cut to the specified length according to markings and the cutting surfaces were grinded.
3	The tolerances were checked: parallel and perpendicular end surfaces, smooth and straight circumferential surface.
4	The diameter and height were measured three times each. The respectively mean value determines the dimensions that are reported.
5	The specimens were then water saturated according to the method described in SKB MD 160.002, version 2.0, (SKB internal controlling document) and were stored for minimum 7 days in water whereupon the wet density was determined.

### 4.3 Mechanical testing

The specimens had been stored for 36–41 days in water when the triaxial compression tests were carried out. The functionality of the triaxial testing system was checked, by performing tests on other cores with a similar rock type before the tests described in this report started. A check-list was filled in successively during the work in order to confirm that the different specified steps had been carried out. Moreover, comments were made upon observations made during the mechanical testing that are relevant for the interpretation of the results. The check-list form is an SP internal quality document.

A step-by step description of the test procedure is as follows.

Step	Activity
1	Digital photos were taken on each specimen prior to the mechanical testing.
2	The specimen was put in testing position and centred between the loading plates.
3	A rubber membrane was mounted on the specimen and the devices for measuring axial and circumferential deformations were attached to the specimen on top of the rubber membrane.
4	The core on each LVDT was adjusted by means of a set screw to the correct initial position. This was done so that the optimal range of the LVDTs can be used for the deformation measurement.
5	The triaxial cell was closed and filled with oil whereby a cell pressure of 0.6 MPa is applied.
6	The frame piston was brought down into contact with the specimen with a force corresponding to a deviatoric stress of 0.6 MPa. The cell pressure was then raised to the specified level and at the same time keeping the deviatoric stress constant.
7	The deformation measurement channels were zeroed in the test software.
8	The loading was started and the initial loading rate was set to a radial strain rate of $-0.025\%/min$ . The loading rate was increased after reaching the post-failure region. This was done in order to prevent the total time for the test to become too long.
9	The test was stopped either manually when the test had proceeded long enough to reveal the post-failure behaviour, or after severe cracking had occurred and it was judged that very little residual axial loading capacity was left in the specimen.
10	The oil pressure was brought down to zero and the oil was poured out of the cell. The cell was opened and the specimen removed.
11	Digital photos were taken on each specimen after the mechanical testing.

## 4.4 Data handling

The test results were exported as text files from the test software and stored in a file server on the SP computer network after each completed test. The main data processing, in which the elastic moduli were computed and the peak stress was determined, has been carried out in the program MATLAB /9/. Moreover, MATLAB was used to produce the diagrams shown in Section 5.1 and in Appendix B. The summary of results in Section 5.2 with tables containing mean value and standard deviation of the different parameters and diagrams were provided using MS Excel. MS Excel was also used for reporting data to the SICADA database.

## 4.5 Analyses and interpretation

As to the definition of the different results parameters we begin with the axial stress  $\sigma_a$ , which is defined as

$$\sigma_a = \frac{F}{A}$$

where  $F$  is the axial force acting on the specimen and  $A$  is the specimen cross section area. Within the pressure vessel (triaxial cell) filled with oil, the specimen is pressurized with a cell (confining) pressure  $p$ . This implies that the specimen becomes confined and the radial stress  $\sigma_r$  of the specimen is equal to confining pressure  $p$ . The (effective) deviatoric stress is defined as

$$\sigma_{\text{dev}} = \sigma_a - \sigma_r$$

The peak value of the axial stress during a test is representing the triaxial compressive strength  $\sigma_c$ , for the actual confining pressure used in the test, see the results presentation.


The average value of the two axial displacement measurements on opposite sides of the specimen is used for the axial strain calculation. The recorded deformation  $\delta_{\text{local}}$  represents a local axial displacement between the points approximately at  $\frac{1}{4}$  and  $\frac{3}{4}$  of the specimen height, cf Figure 4-1. The axial strain is defined as

$$\varepsilon_a = \delta_{\text{local}}/L_{\text{local}}$$

where  $L_{\text{local}}$  is the distance between the rings before loading.

The radial deformation is measured by means of a chain mounted around the specimen at mid-height, see Figure 3-2. The change of chain opening gap is measured by means of one LVDT. This measurement is used to compute the radial strain  $\varepsilon_r$ , see Appendix A. Moreover, the volumetric strain  $\varepsilon_{\text{vol}}$  is defined as

$$\varepsilon_{\text{vol}} = \varepsilon_a + 2\varepsilon_r$$

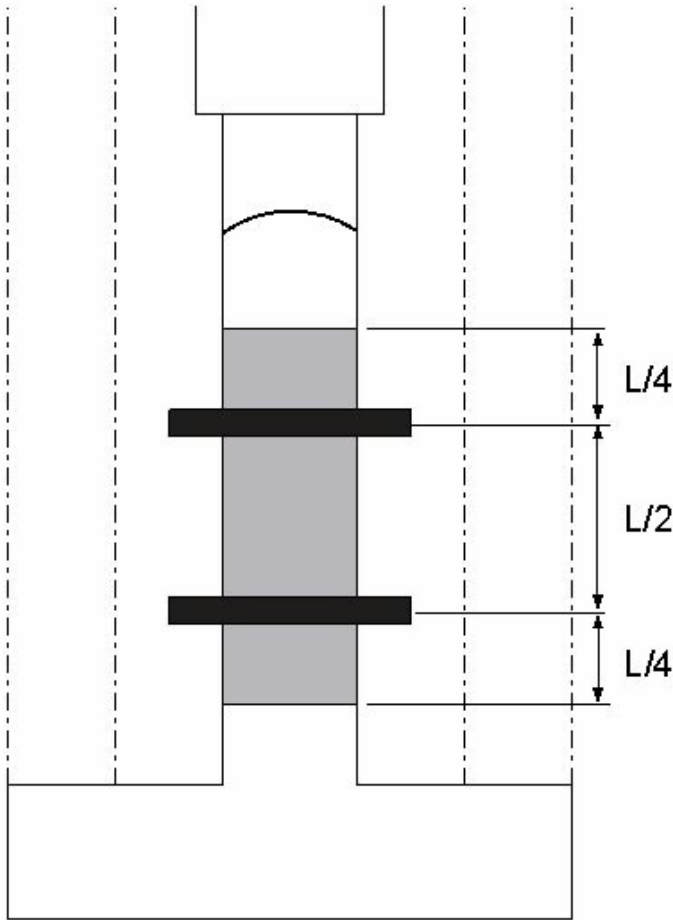

**Figure 4-1.** Sketch showing the triaxial cell with the rock specimen (grey) with height  $L$  and the position of the rings (black) used for the axial deformation measurements. The membrane is omitted in the figure for simplicity.

The stresses and the strains are defined as positive in compressive loading and deformation. The elasticity parameters are defined by the tangent Young's modulus  $E$  and tangent Poisson ratio  $\nu$  as

$$E = \frac{\sigma_a(0.60\sigma_c) - \sigma_a(0.40\sigma_c)}{\varepsilon_a(0.60\sigma_c) - \varepsilon_a(0.40\sigma_c)}$$

$$\nu = -\frac{\varepsilon_r(0.60\sigma_c) - \varepsilon_r(0.40\sigma_c)}{\varepsilon_a(0.60\sigma_c) - \varepsilon_a(0.40\sigma_c)}$$

The tangents were evaluated with values corresponding to an axial load between 40% and 60% of the axial peak stress  $\sigma_c$ .

A closure of present micro cracks will take place initially during confinement and axial loading. Development of new micro cracks will start when the axial load is further increased and axial stress reaches the crack initiation stress  $\sigma_i$ . The crack growth at this stage is as stable as increased loading is required for further cracking. A transition from a development of micro cracks to macro cracks will take place when the axial load is further increased. At a certain stress level the crack growth becomes unstable. The stress level when this happens is denoted the crack damage stress  $\sigma_d$ , cf /2, 3/. In order to determine the stress levels we look at the volumetric strain.

By subtracting the elastic volumetric strain  $\varepsilon_{\text{vol}}^e$  from the total volumetric strain a volumetric strain corresponding to the crack volume is obtained  $\varepsilon_{\text{vol}}^{\text{cr}}$ . This has been denoted calculated crack volumetric strain in the literature, cf /2, 3/. We thus have

$$\varepsilon_{\text{vol}}^{\text{cr}} = \varepsilon_{\text{vol}} - \varepsilon_{\text{vol}}^e$$

Assuming linear elasticity leads to

$$\varepsilon_{\text{vol}}^{\text{cr}} = \varepsilon_{\text{vol}} - \frac{1-2\nu}{E}(\sigma_a - \sigma_r)$$

Experimental investigations have shown that the crack initiation stress  $\sigma_i$  coincides with the onset of increase of the calculated crack volume, cf /2, 3/. The same investigations also indicate that the crack damage stress  $\sigma_d$  can be defined as the axial stress at which the total volume starts to increase, i.e. when a dilatant behaviour is observed.

## 4.6 Nonconformities

The testing was conducted according to the method description except for one deviation. The circumferential strains have been determined within a relative error of 1.5%, which is larger than what is specified in the ISRM-standard /1/.

Otherwise, the activity plan was followed with no departures except for that the specimen KFM05A-115-9 was replaced by specimen KFM05A-115-10.

## **5 Results**

The results of the individual specimens are presented in Section 5.1 and a summary of the results is given in Section 5.2. The reported parameters are based on unprocessed raw data obtained from the testing and were reported to the SICADA database where data are traceable by the activity plan number. These data together with the digital photographs of the individual specimens were stored on a CD and handed over to SKB. The handling of the results follows SDP-508 (SKB internal controlling document) in general.

### **5.1 Description and presentation of the specimen**


The cracking is shown in pictures taken on the specimens with comments on observations made during the testing. The elasticity parameters have been evaluated by using the results from the local deformation measurements. Red rings are superposed on the graphs indicating every five minutes of the progress of testing. The results for the individual specimens are as follows:



**Specimen ID:** KFM05A-115-1

Before mechanical test

After mechanical test

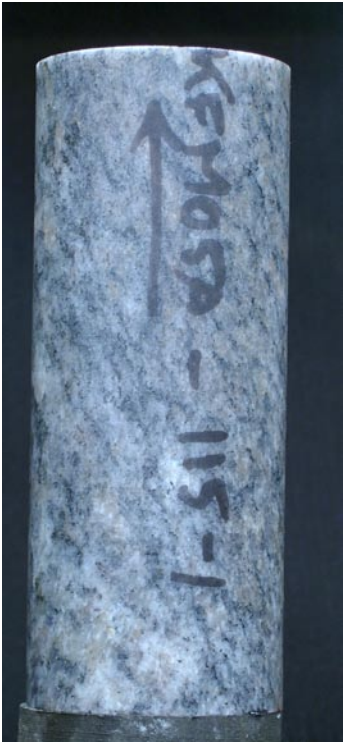



<b>Diameter (mm)</b>	<b>Height (mm)</b>	<b>Density (kg/m<sup>3</sup>)</b>
50.7	127.1	2,640
<b>Comments</b>	Shear type of failure with overlaid horizontal cracks.	

Specimen ID: KFM05A-115-01

Youngs Modulus (E): 77.7 [GPa]


Poisson Ratio ( $\nu$ ): 0.163 [-]

Axial peak stress ( $\sigma_p$ ): 360.5 [MPa]

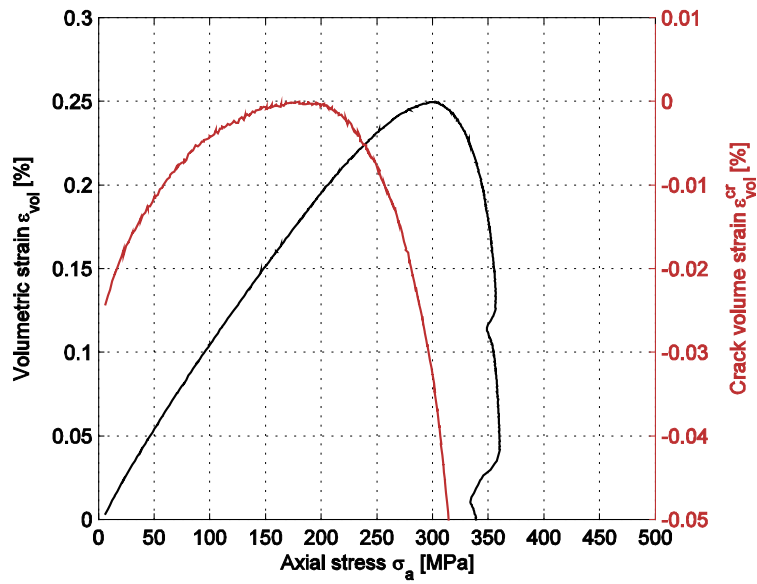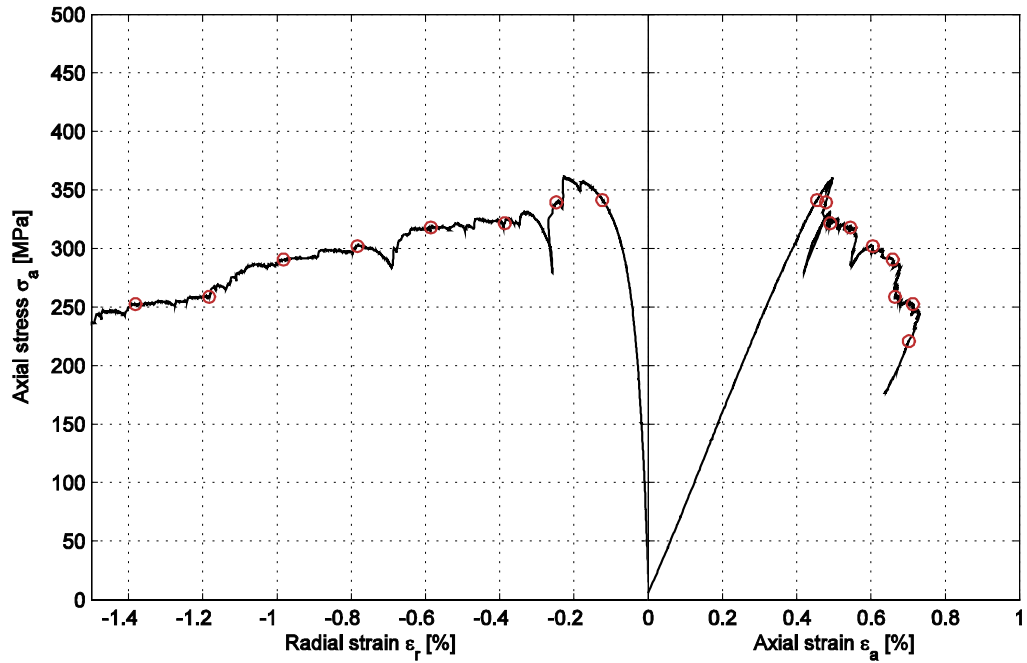

**Specimen ID:** KFM05A-115-2

Before mechanical test

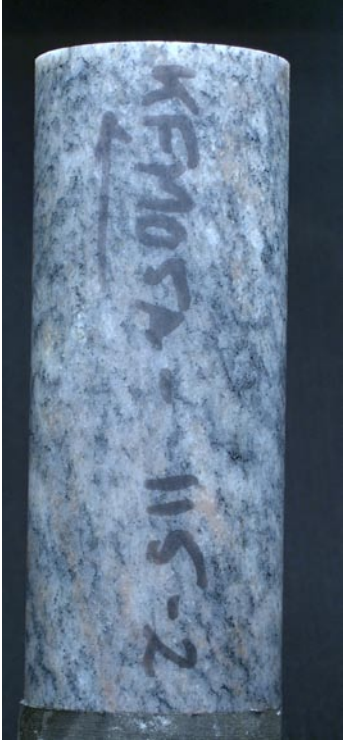

After mechanical test





<b>Diameter (mm)</b>	<b>Height (mm)</b>	<b>Density (kg/m<sup>3</sup>)</b>
50.7	127.2	2,590
<b>Comments</b>	V-shaped shear failure.	

Specimen ID: KFM05A-115-02

Youngs Modulus (E): 77.8 [GPa]

Poisson Ratio ( $\nu$ ): 0.203 [-]

Axial peak stress ( $\sigma_c$ ): 410.2 [MPa]

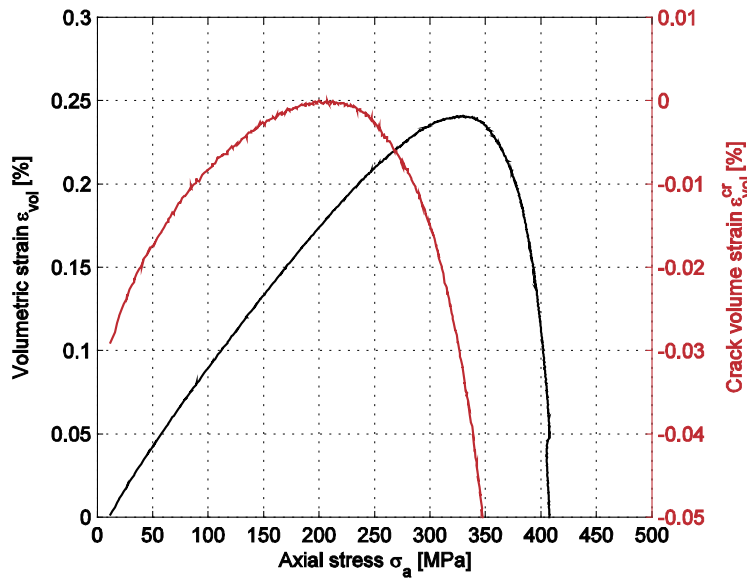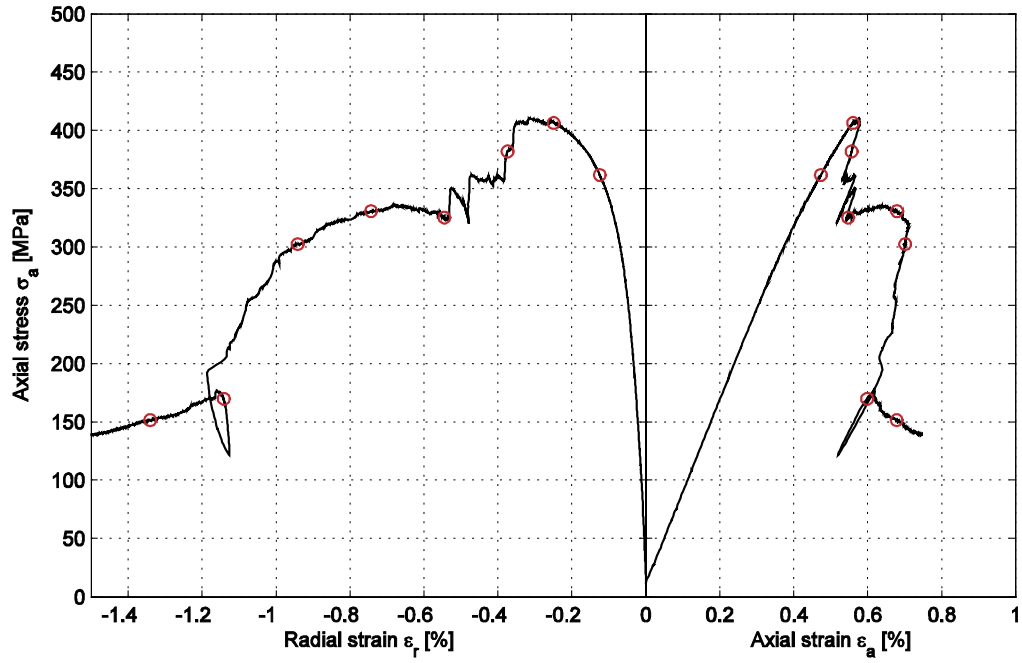

**Specimen ID:** KFM05A-115-3

Before mechanical test



After mechanical test





<b>Diameter (mm)</b>	<b>Height (mm)</b>	<b>Density (kg/m<sup>3</sup>)</b>
50.7	127.2	2,610
<b>Comments</b>	Diagonal shear failure.	

Specimen ID: KFM05A-115-03

Youngs Modulus (E): 76.4 [GPa]

Poisson Ratio ( $\nu$ ): 0.17 [-]

Axial peak stress ( $\sigma_c$ ): 345.6 [MPa]

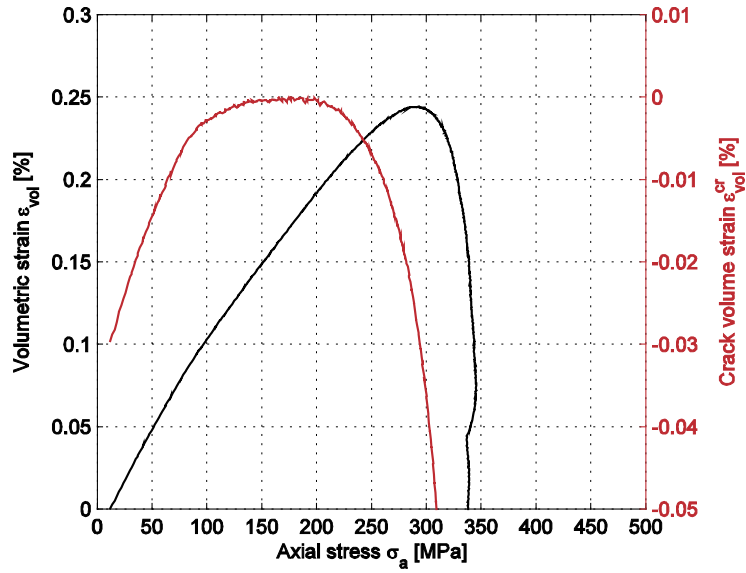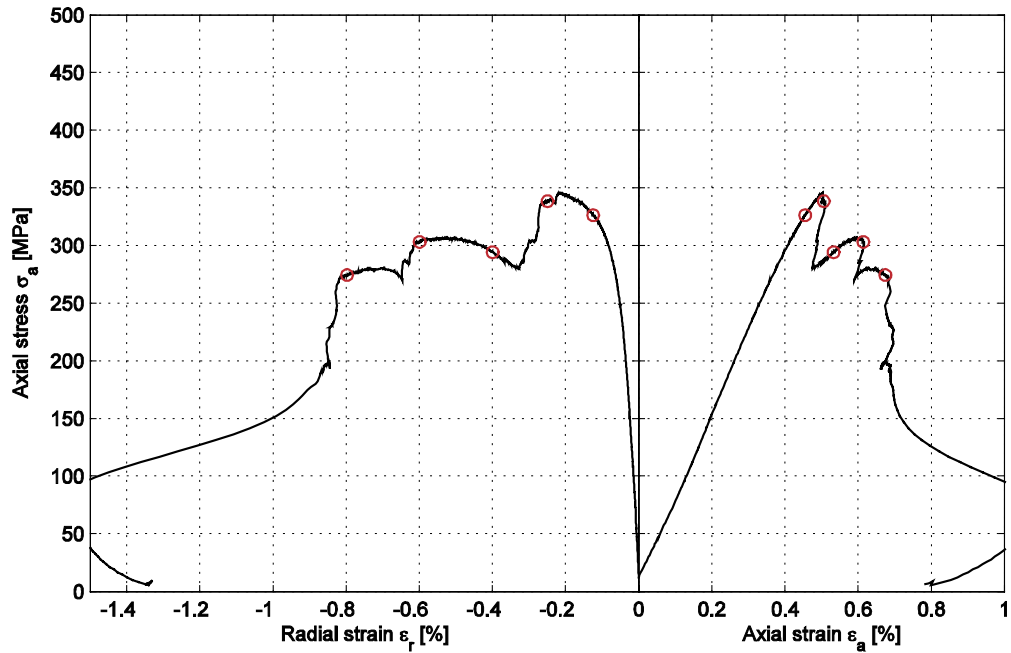

Specimen ID: KFM05A-115-4

Before mechanical test

After mechanical test





<b>Diameter (mm)</b>	<b>Height (mm)</b>	<b>Density (kg/m<sup>3</sup>)</b>
50.7	127.1	2,710
<b>Comments</b>	Diagonal shear failure. The membrane was punctured.	

**Specimen ID: KFM05A-115-04**

Youngs Modulus (E): 78.5 [GPa]

Poisson Ratio ( $\nu$ ): 0.198 [-]

Axial peak stress ( $\sigma_c$ ): 462.8 [MPa]

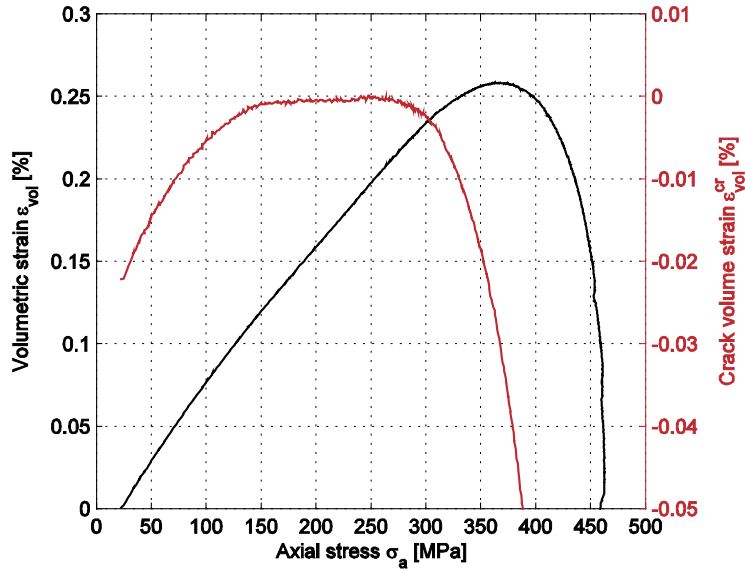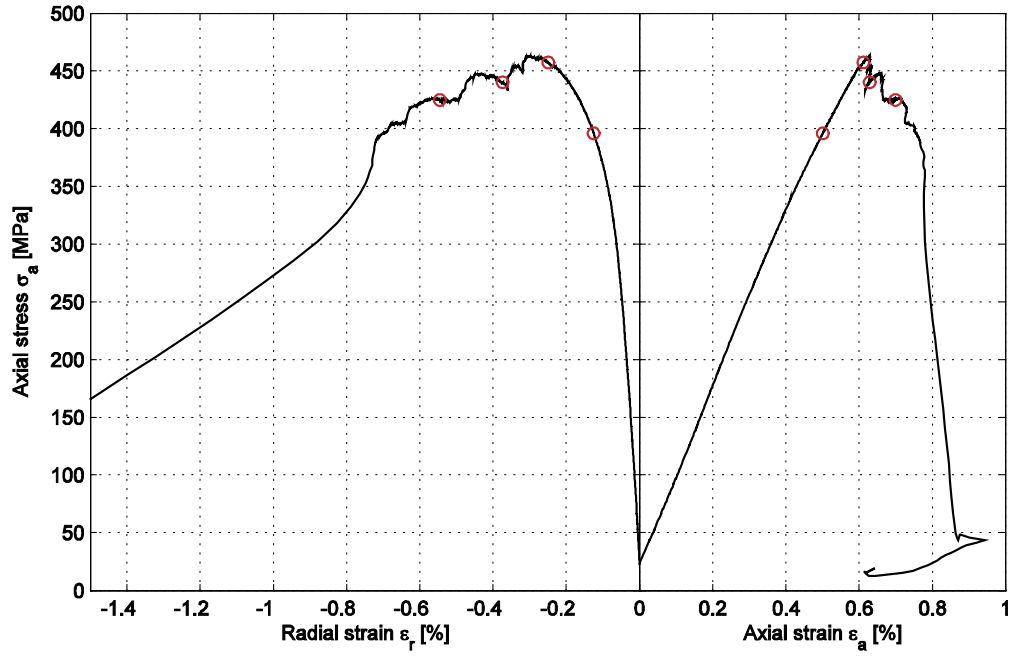



Specimen ID: KFM05A-115-6

Before mechanical test

After mechanical test



Diameter (mm)	Height (mm)	Density (kg/m <sup>3</sup> )
50.6	127.2	2,660



**Comments** Diagonal major shear failure and some minor cracks are observed. The cracks follow the diagonally oriented foliation.

Specimen ID: KFM05A-115-06

Youngs Modulus (E): 75 [GPa]

Poisson Ratio ( $\nu$ ): 0.151 [-]


Axial peak stress ( $\sigma_c$ ): 289.2 [MPa]

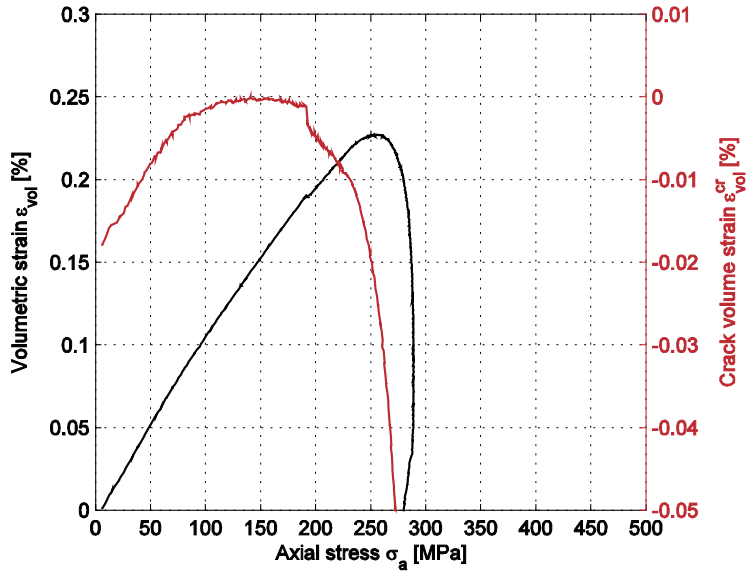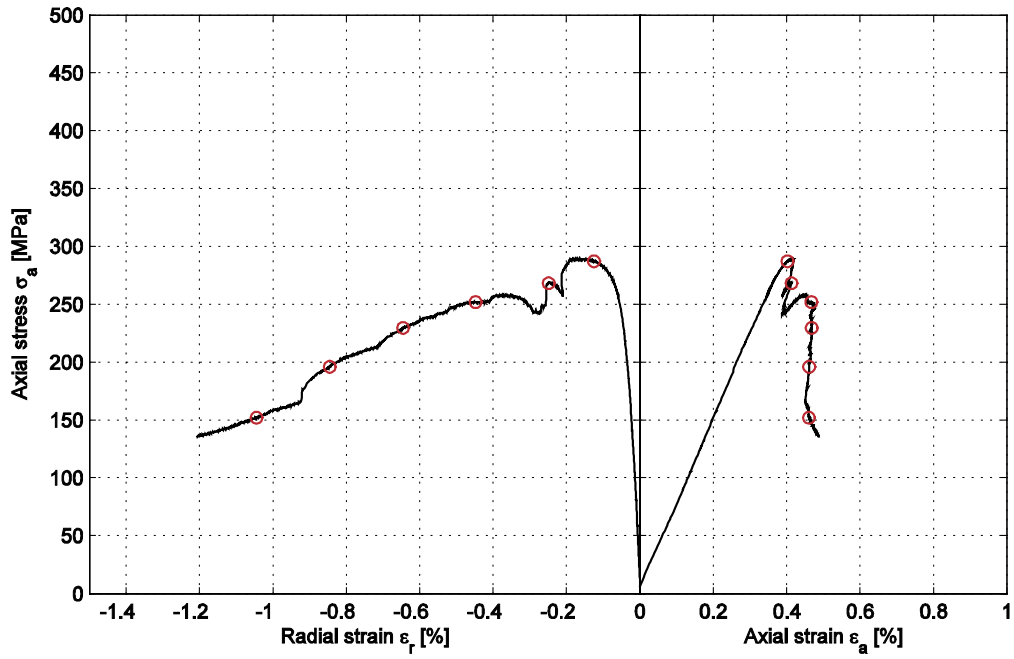

**Specimen ID:** KFM05A-115-7

Before mechanical test

After mechanical test

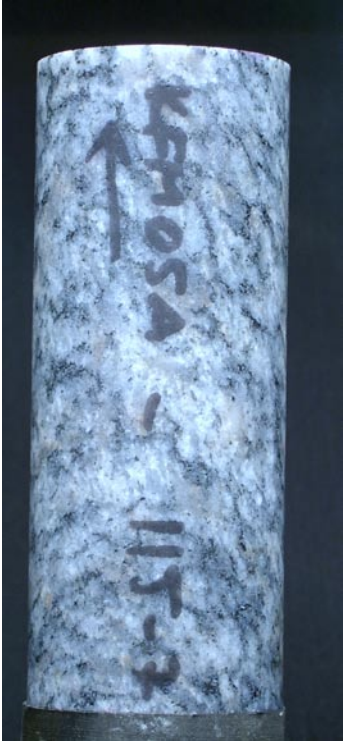



<b>Diameter (mm)</b>	<b>Height (mm)</b>	<b>Density (kg/m<sup>3</sup>)</b>
50.6	127.1	2,650
<b>Comments</b>	Diagonal shear failure.	

Specimen ID: KFM05A-115-07

Youngs Modulus (E): 77.9 [GPa]

Poisson Ratio ( $\nu$ ): 0.183 [-]

Axial peak stress ( $\sigma_p$ ): 355.8 [MPa]

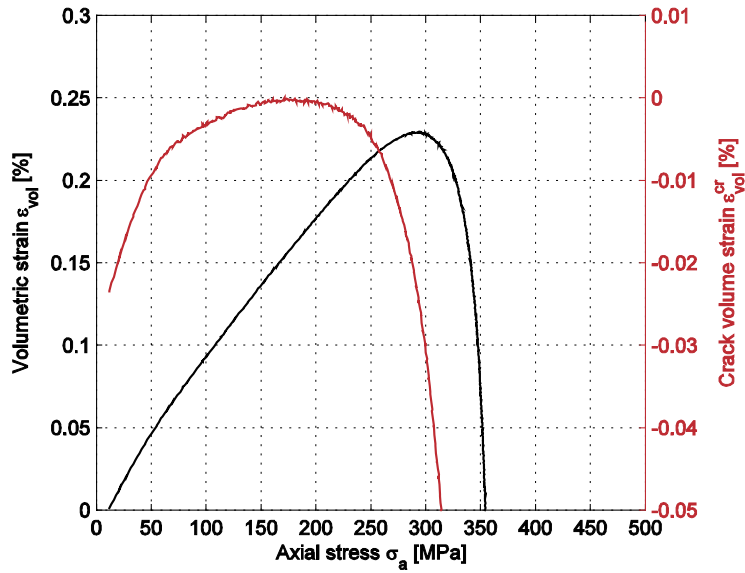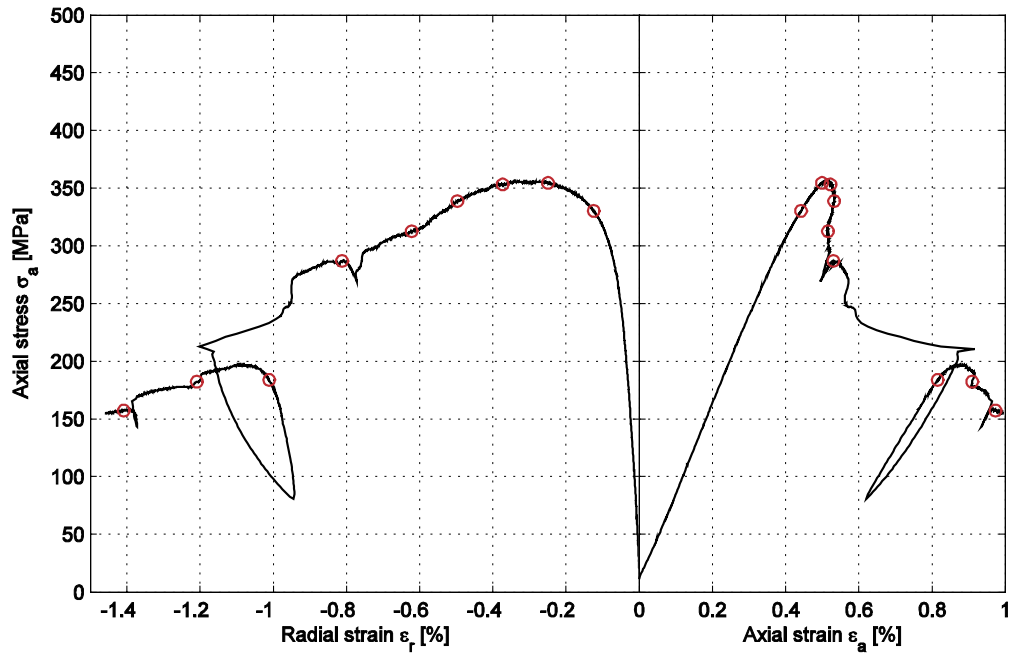

**Specimen ID:** KFM05A-115-8

Before mechanical test



After mechanical test





<b>Diameter (mm)</b>	<b>Height (mm)</b>	<b>Density (kg/m<sup>3</sup>)</b>
50.6	127.2	2,660
<b>Comments</b>	Diagonal shear failure.	

Specimen ID: KFM05A-115-08

Youngs Modulus (E): 85.4 [GPa]

Poisson Ratio ( $\nu$ ): 0.195 [-]

Axial peak stress ( $\sigma_p$ ): 354.2 [MPa]

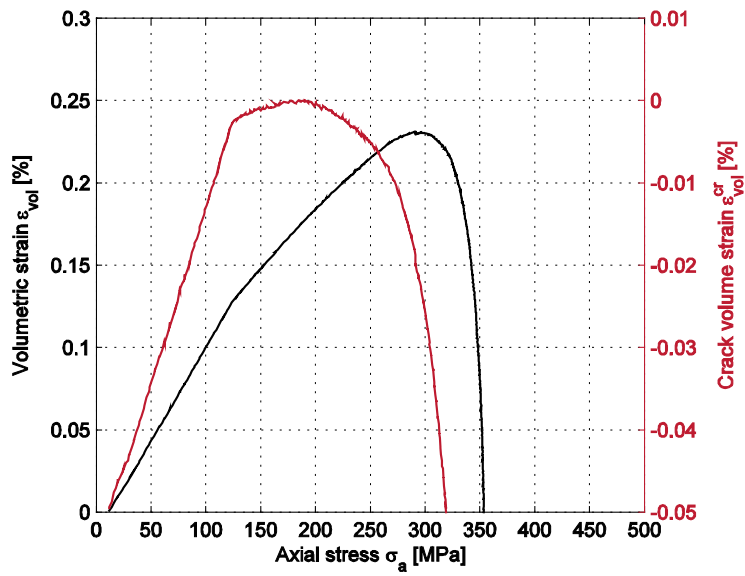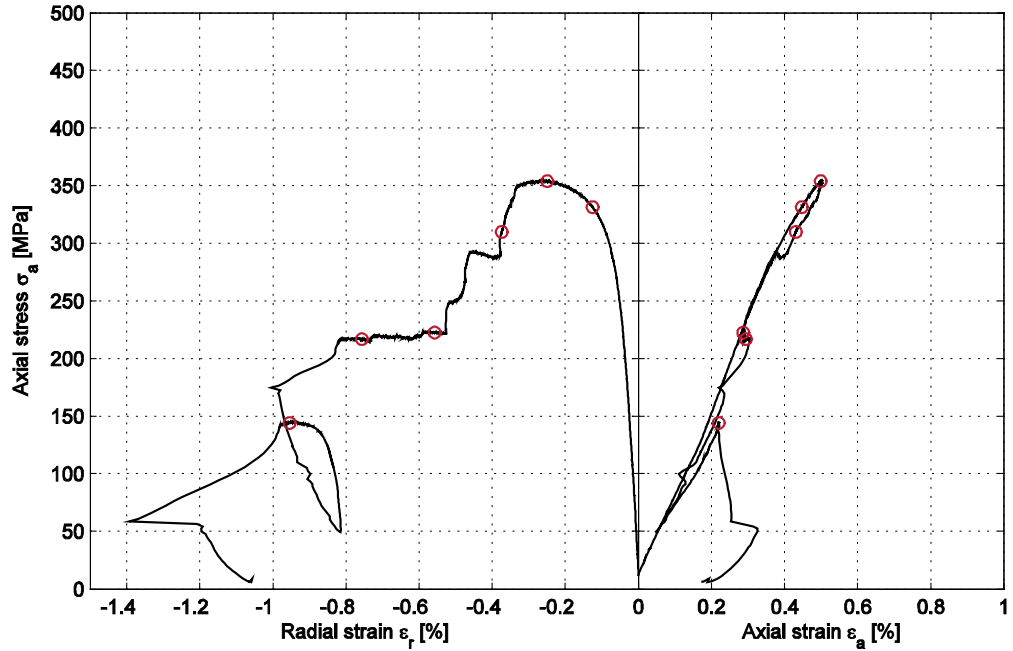

**Specimen ID:** KFM05A-115-10

Before mechanical test

After mechanical test





<b>Diameter (mm)</b>	<b>Height (mm)</b>	<b>Density (kg/m<sup>3</sup>)</b>
50.8	127.2	2,660
<b>Comments</b>	V-shaped shear failure. The membrane was punctured.	

**Specimen ID: KFM05A-115-10**

Youngs Modulus (E): 81.8 [GPa]

Poisson Ratio ( $\nu$ ): 0.182 [-]

Axial peak stress ( $\sigma_p$ ): 488.5 [MPa]

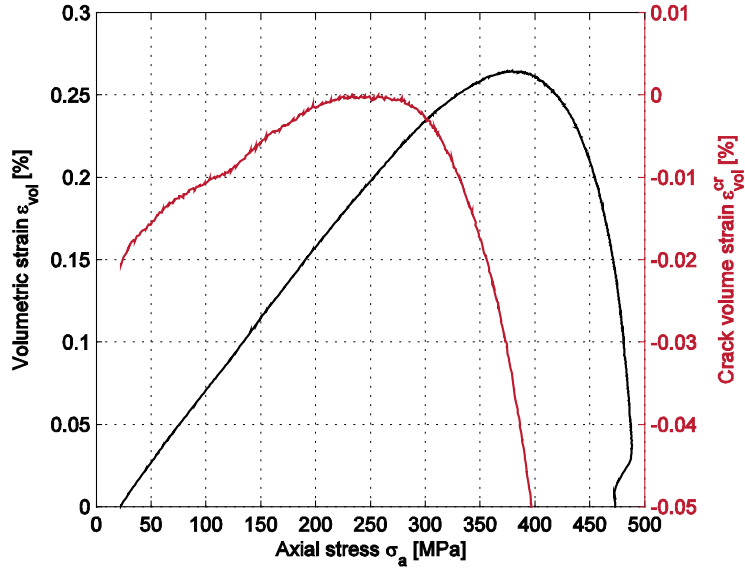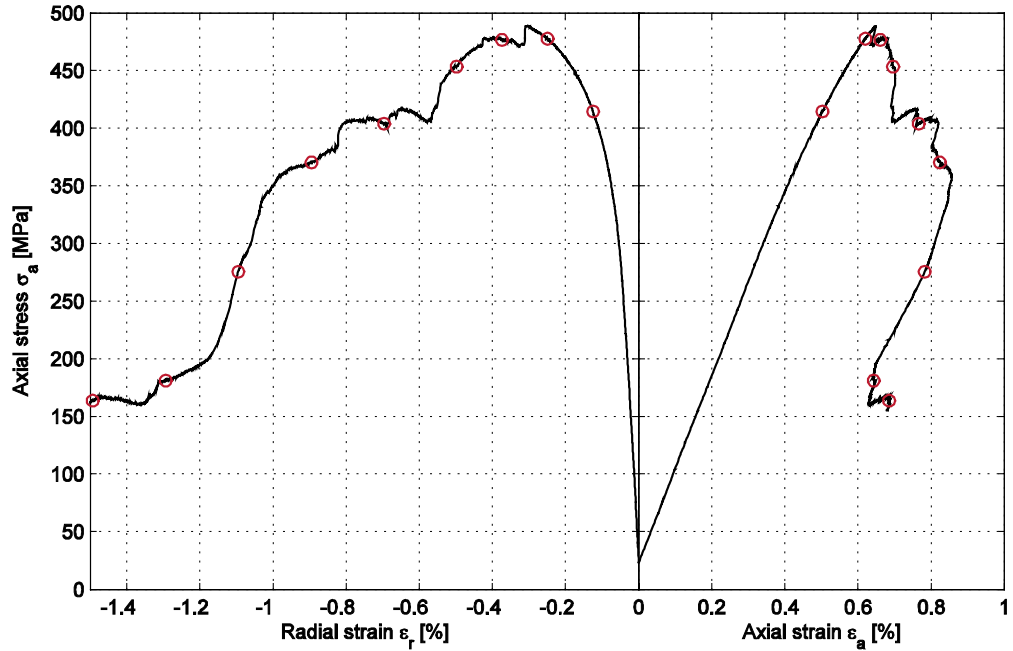



## 5.2 Results for the entire test series


A summary of the test results is shown in Tables 5-1 and 5-2. The densities, triaxial compressive strength, the tangent Young's modulus and the tangent Poisson ratio versus the depth, at which the specimens are taken, are shown in Figures 5-1 to 5-4.

**Table 5-1. Summary of results.**

Identification	Conf press (MPa)	Density (kg/m <sup>3</sup> )	Compressive Strength (MPa)	Young's modulus (GPa)	Poisson ratio (-)	Comments
KFM05A-115-1	5	2,640	360.5	77.7	0.16	
KFM05A-115-2	10	2,590	410.2	77.8	0.20	
KFM05A-115-3	10	2,610	345.6	76.4	0.17	
KFM05A-115-4	20	2,710	462.8	78.5	0.20	
KFM05A-115-6	5	2,660	289.2	75.0	0.15	
KFM05A-115-7	10	2,650	355.8	77.9	0.18	
KFM05A-115-8	10	2,660	354.2	85.4	0.20	
KFM05A-115-10	20	2,660	488.5	81.8	0.18	

**Table 5-2. Calculated mean values and standard deviation.**

	Density (kg/m <sup>3</sup> )	Young's modulus (GPa)	Poisson ratio (-)
Mean value	2,648	78.8	0.18
Standard deviation	36.2	3.3	0.02

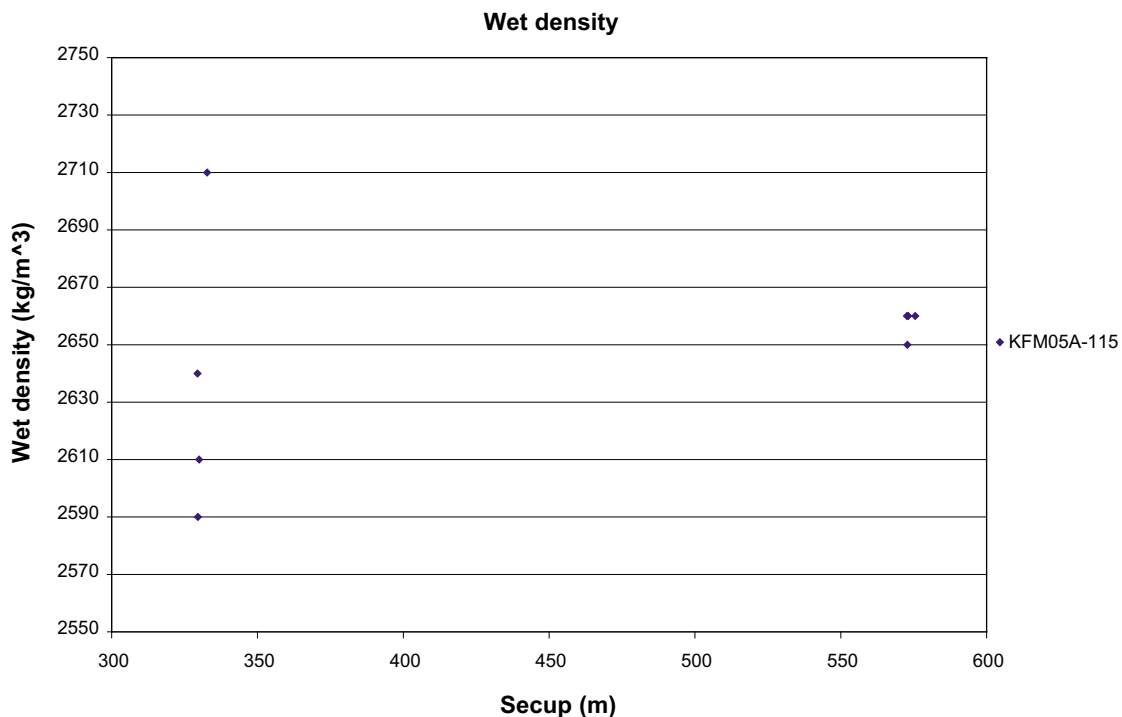

**Figure 5-1. Density versus borehole length.**

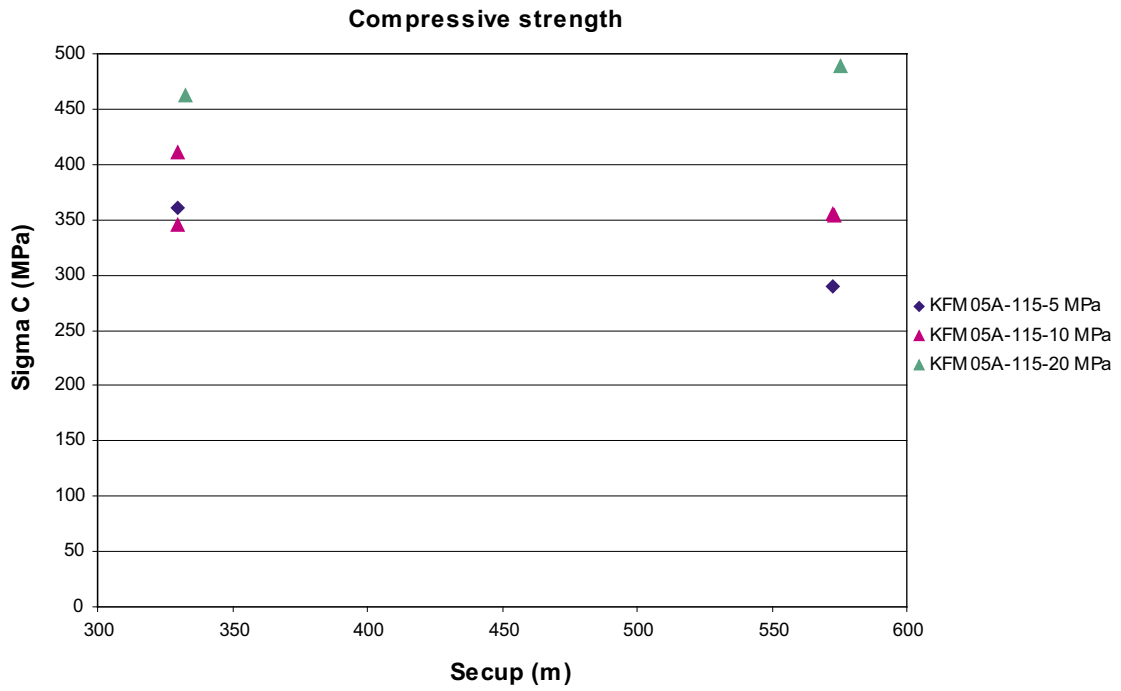


Figure 5-2. Compressive strength versus borehole length.


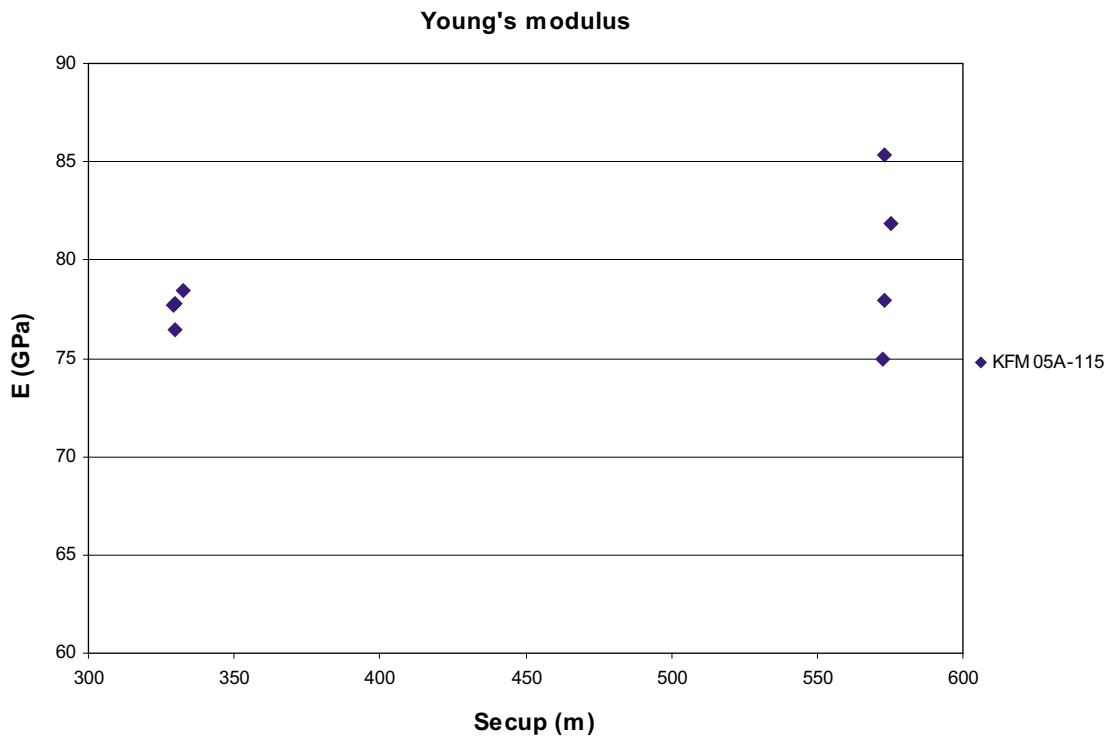


Figure 5-3. Tangent Young's modulus versus borehole length.

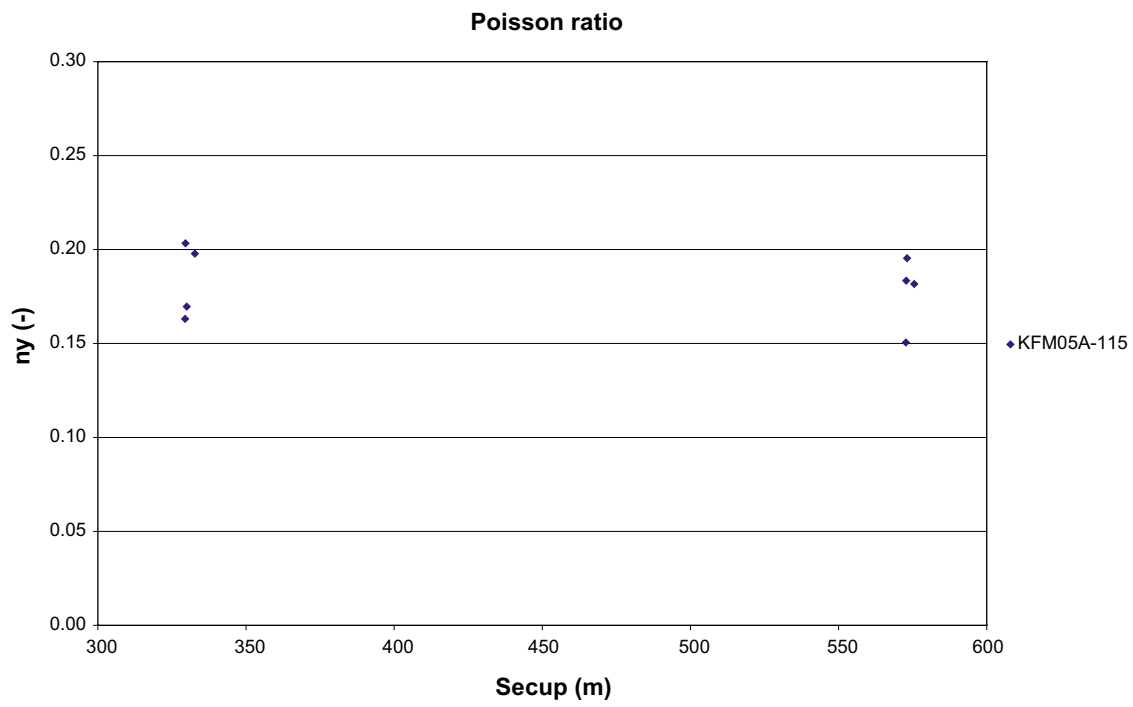

*Figure 5-4. Tangent Poisson ratio versus borehole length.*

## References

- /1/ **ISRM**. Draft ISRM suggested method for the complete stress-strain curve for intact rock in uniaxial compression, *Int. J. Rock. Mech. Min. Sci.* 36(3), pp. 279–289, 1999.
- /2/ **Martin C. D. and Chandler N. A.** The progressive fracture of Luc du Bonnet granite, *Int. J. Rock. Mech. Min. Sci. & Geomech. Abstr.* 31(6), pp. 643–659, 1994.
- /3/ **Eberhardt E, Stead D, Stimpson B, and Read R. S.** Identifying crack initiation and propagation thresholds in brittle rock. *Can. Geotech. J.* 35, pp. 222–233, 1998.
- /4/ **ASTM 4543-01**. Standard practice for preparing rock core specimens and determining dimensional and shape tolerance, 2001.
- /5/ **ISRM**. Suggested Method for Determining Water Content. Porosity, Density, Absorption and Related Properties and Swelling and Slake-durability Index Properties, *Int. J. Rock. Mech. Min. Sci. & Geomech. Abstr.* 16(2), pp. 141–156, 1979.
- /6/ **SS-EN 13755**. Natural stone test methods – Determination of water absorption at atmospheric pressure.
- /7/ **ISRM**. suggested method for determining the strength of rock material in triaxial compression: Revised version, *Int. J. Rock. Mech. Min. Sci. & Geomech. Abstr.* 20(6), pp. 283–290, 1983.
- /8/ **Stråhle A, 2001**. Definition och beskrivning av parametrar för geologisk, geofysisk och bergmekanisk kartering av berg. SKB R-01-19, Svensk Kärnbränslehantering AB.
- /9/ **MATLAB**. The Language of Technical computing. Version 6.5. MathWorks Inc. 2002.

## Appendix A

The following equations describe the correct calculation of radial strains when using a circumferential deformation device, see Figure A-1.

$$\varepsilon_r = \frac{\Delta C}{C_i}$$

where

$C_i = 2 \pi R_i$  = initial specimen circumference

$$\Delta C = \text{change in specimen circumference} = \frac{\pi \cdot \Delta X}{\sin\left(\frac{\theta_i}{2}\right) + \left(\pi - \frac{\theta_i}{2}\right) \cos\left(\frac{\theta_i}{2}\right)}$$

and


$\Delta X$  = change in LVDT reading =  $X_i - X_f$  ( $X_i$  = initial chain gap;  $X_f$  = current chain gap)

$\theta_i$  = initial chord angle =  $2\pi - \frac{L_c}{R_i + r}$

$L_c$  = chain length (measured from center of one end roller to center of the other end roller)

$r$  = roller radius

$R_i$  = initial specimen radius

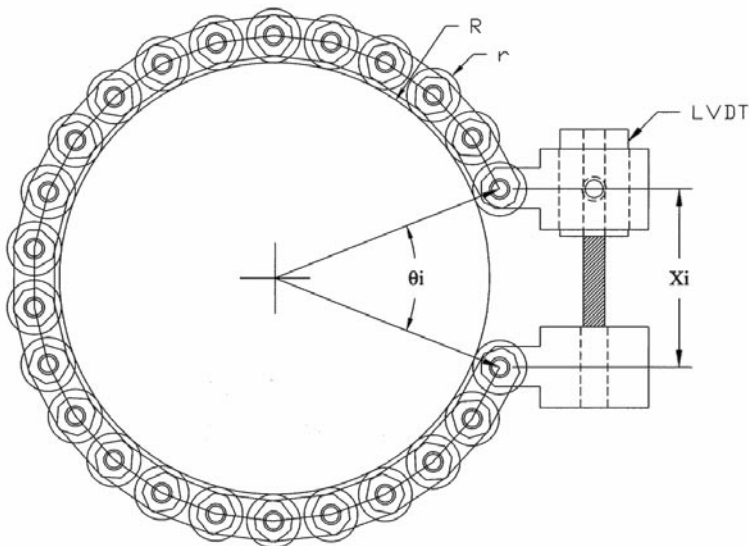


**Figure A-1.** Chain for radial deformation measurement.


## Appendix B

This appendix contains complementary results showing the volumetric strain  $\varepsilon_{vol}$  versus the axial strain  $\varepsilon_a$  and the actual radial strain rate  $d\varepsilon_r/dt$  versus time. The complementary results for all tests are shown below.


Specimen ID: KFM05A-115-01

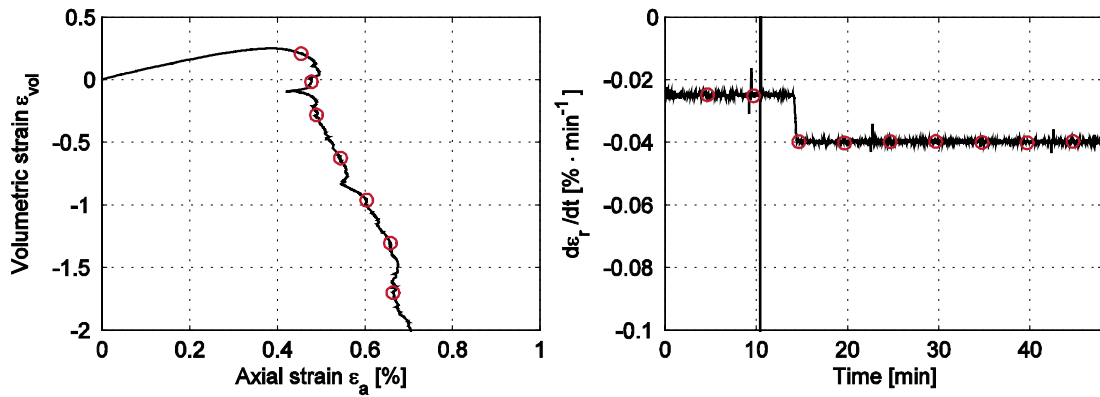



Specimen ID: KFM05A-115-02

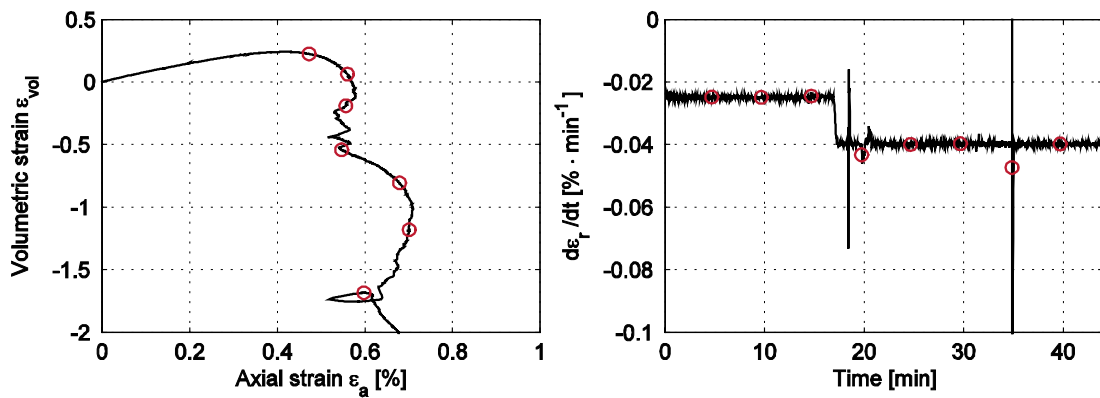



Specimen ID: KFM05A-115-03

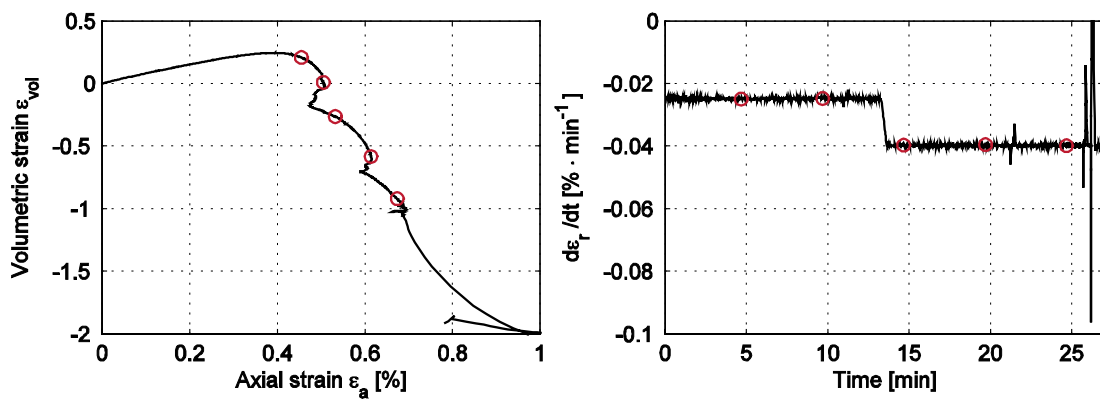



Specimen ID: KFM05A-115-04

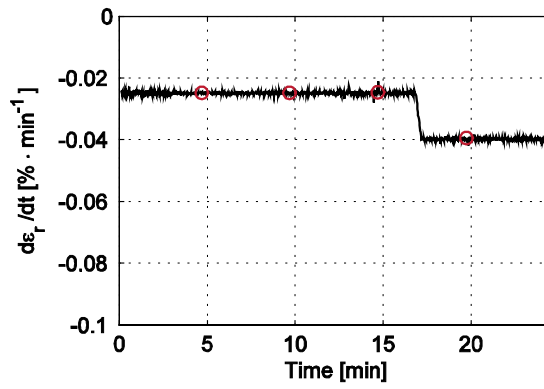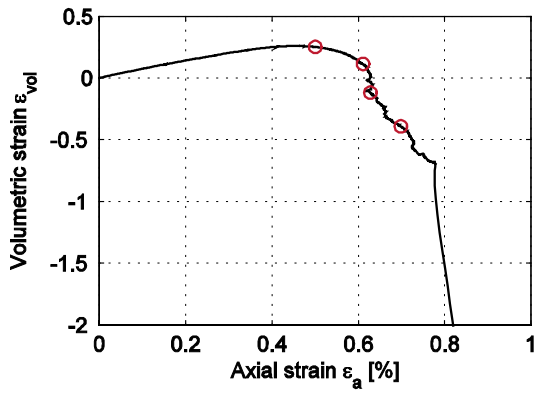



Specimen ID: KFM05A-115-06

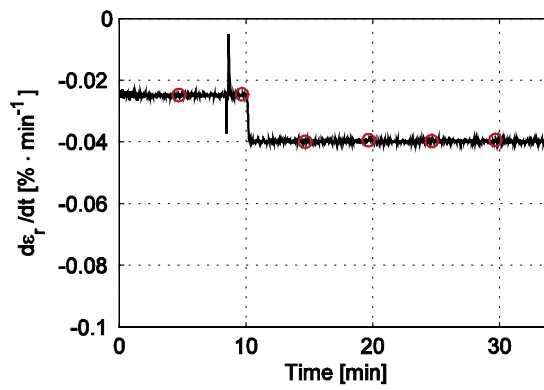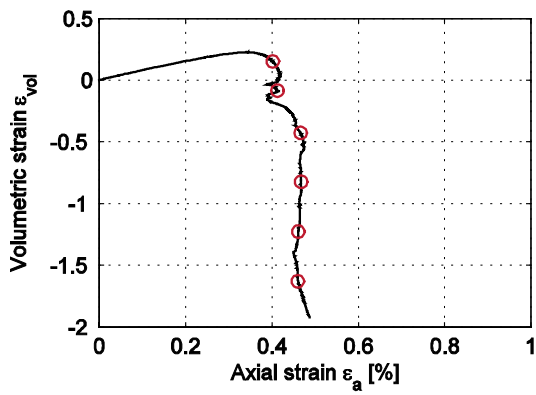

Specimen ID: KFM05A-115-07

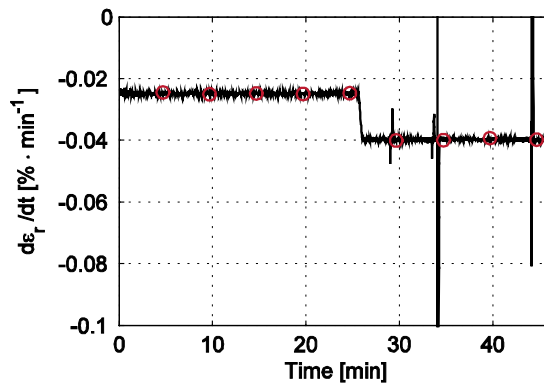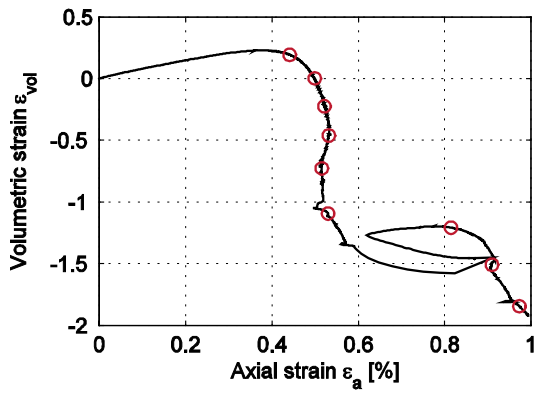

Specimen ID: KFM05A-115-08

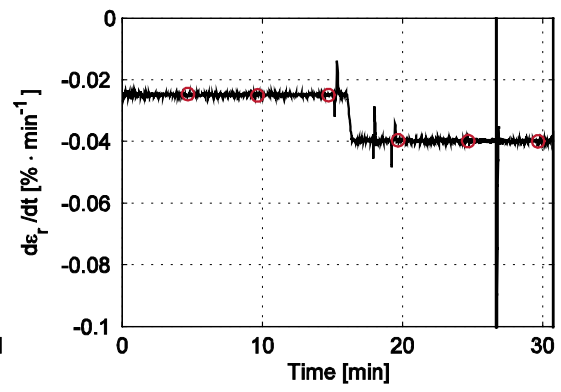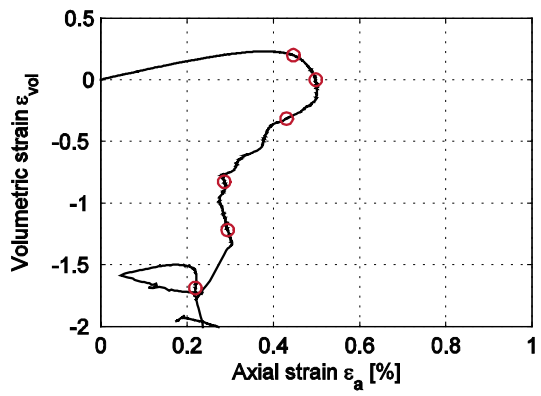

Specimen ID: KFM05A-115-10

